

Green Approach to Corrosion Inhibition of Mild Steel using Emilia Sonchifolia and Vitex Doniana in 2.5M HCl Medium

Iloamaeke I. M., Onuegbu T. U., Umeobika U. C., Umedum N. L.

Abstract: This research studied the use of leaves extract of *Emilia sonchifolia* and *Vitex doniana* as corrosion inhibitors of mild steel in 2.5M HCl medium using gasometric method at 30°C and 60°C. The result obtained showed that inhibition efficiency of *Emilia sonchifolia* leaves extract on the surface of the mild steel was 60.38% at 30°C and 53.13% at 60°C while that of *Vitex doniana* leave extract was 68.22% at 30°C and 54.98% at 60°C. Adsorption of *Emilia sonchifolia* leaves extract on the surface of the mild steel follows Langmuir, Tempkin and Freundlich adsorption isotherm while adsorption of *Vitex doniana* leaves extract on the surface of the mild steel obeyed Langmuir and Tempkin adsorption isotherm. Physical adsorption was proposed from the E_a , ΔH and ΔG calculated.

Key words; corrosion, inhibitor, mild steel, *Emilia sonchifolia* and *Vitex doniana*

I. INTRODUCTION

Corrosion is the disintegration of an engineering material into its constituent atom due to chemical reaction with its surroundings or electrochemical oxidation of metal in reaction with an oxidant such as oxygen [1]. Typically, this type of damage produces oxide or salts of the original metal. Corrosion is a costly problem that results to economic waste when referring to cost of design, manufacturing, construction and management. This bitter aspect of corrosion is experienced mostly by the industries that are making use of mild steel especially chemical and allied industries. Mitigation of this problem of corrosion lies on the use of corrosion inhibitors, which help to prolong the life span of these materials. The use of synthetic inhibitors like chromium, cadmium, and lead based compound are considered as environmentally unsafe, because these elements are heavy metals [2]. Therefore, research is now geared towards using plant extract as corrosion inhibitors because they are non toxic, environmental friendly, easily biodegradable and renewable.

Manuscript received on February, 2013.

Iloamaeke I. M., Chemistry Department ,Nnamadi university Awka. Anambra State. Nigeria.

Onuegbu T.U., Chemistry Department ,Nnamadi university Awka. Anambra State. Nigeria.

Umeobika U.C., Chemistry Department ,Nnamadi university Awka. Anambra State. Nigeria.

Umedum N.L., Chemistry Department ,Nnamadi university Awka. Anambra State. Nigeria.

The list of works done on the use of plants extract as corrosion inhibitors are endless, to mention but few are extract of fengrech seed and leave [3], L.Dopa [4], Azadiracta indica [5], Citrus aurantifolia [6] Pterocarpus soyauxi [7], Emblica officinalis (Indian Gooseberry) [8], Ricinus communis [9], Nypa fruticans wurmb [10], Tecoma stans [11], Blackpapper [12], Capparius decidua [13], Nyctanthes arbotis [14] and Kalmegh (andrographis paniculata)[15].

The aim of this research is to compare the inhibitory action of *Emilia sonchifolia* (ES) and *Vitex doniana* (VD) on the surface of the mild steel using gasometric method at 30°C and at 60°C.

II. MATERIAL AND METHOD

A. Preparation of *Emilia sonchifolia* and *Vitex doniana* leaves extract:

1500g of *Emilia sonchifolia* leaves (ES) and 1500g of *Vitex doniana* leaves (VD) was air dried in a shade for 8-12 days and ground into powder. 350g of the powder was taken in 1000ml round bottom flask and enough quantity of ethanol was added as a solvent for extraction. The round bottom flask was covered with a stopper and left for 48hrs. Then the resulting paste was refluxed for 5hrs and filtered. The solvent was removed by concentrating the filtrate to about 20%. From this 0.1-0.5g/l concentration was made.

B. Specimen preparation:

Mild steel of thickness 1.4mm was obtained locally and was mechanically cut into coupons of 3×2×0.14cm. A small hole was drilled at one end of the coupons for easy hooking. The coupons were degreased in absolute ethanol, dried in acetone and stored in a desiccator.

C. Test solution preparation:

All the chemicals used were of Analytical grade. Solution was prepared by using double distilled water, and different concentrations of 1.0M – 2.5M HCl were prepared.

III. GASOMETRIC METHOD

Mild steel of 2 x 3 x 0.144cm was used here and this experiment was carried out at 30°C and 60°C. The procedure for this experiment has been documented in literature [16]-[18]. From the volume of hydrogen evolved per minute, inhibition efficiency (I %) and degree of surface coverage (θ) were calculated using equation 1 & 2

$$I(\%) = \left(1 - \frac{V^1Ht}{V^0Ht}\right) \times 100 \quad (1)$$

$$\theta = 1 - \frac{V_{Ht}^1}{V_{Ht}^0} \quad (2)$$

Where V_{Ht}^1 and V_{Ht}^0 are the volume of H_2 gas evolved at time t for inhibited and uninhibited solution respectively. Rate of hydrogen evolution was computed using equation 3 [19]

$$H_R = \frac{V_t - V_i}{T_t - T_i} \quad (3)$$

Where H_R is the rate of hydrogen evolution, V_t and V_i are the volume of hydrogen evolved at time T_t and T_i respectively.

IV. RESULTS AND DISCUSSION

Table 1 shows different concentrations of the ES and VD extract and inhibition efficiency. It could be deduced from the table that inhibition efficiency increase as the concentrations of the both extract increase with decrease in temperature inferring physical adsorption of the ES and VD extract on the surface of the mild steel.

V. ADSORPTION CONSIDERATION

The adsorption behavior of ES and VD extract was also studied. The test revealed that adsorption of ES extract on the surface of the mild steel is consistent with the Langmuir, Tempkin and Freundlich adsorption Isotherms. While the adsorption of VD extract on the surface of the mild steel obeyed Langmuir and Tempkin adsorption isotherms. Langmuir adsorption models can be represented as follows equation 6 [20]

$$\frac{C}{\theta} = C + \frac{1}{k} \quad (4)$$

Taking the logarithm of equation 4, equation 5 is obtained $\log C/\theta = \log C - \log K$ (5)

Where C is the concentration of the inhibitor in the electrolyte, θ is the degree of surface coverage of the inhibitor and k is the equilibrium constant of adsorption. The plot of C/θ versus C (fig 1 and 2) gave linear plots indicating that Langmuir adsorption isotherm is applicable to the adsorption of ethanol extract of ES and VD on the surface of the mild steel.

Tempkin isotherm was also found to occur according to this equation 6 [21]–[22]

$$\text{Exp}(-2a\theta) = k \quad (6)$$

Where “ a ” is the Tempkin interaction parameter, θ is the degree of surface coverage of the inhibitor. K is the equilibrium constant of adsorption and C is the concentration of the inhibitor in the bulk electrolyte. Rearranging and taking logarithm of equation 6, equation 7 is obtained.

$$\theta = \frac{-2.303 \log K}{2a} - \frac{2.303 \log C}{2a} \quad (7)$$

Slope = $-\frac{2.303}{2a}$, Intercept = $-\frac{2.303 \log k}{2a}$

Fig.3 and 4: Shows plot of θ versus $\log C$. which was made from equation 6 and a linear graph was obtained which confirmed Tempkin adsorption isotherm for the adsorption of ES and VD extract on the surface of mild steel. Fig.5 revealed Freundlich’s adsorption isotherm of the extract of ES on the surface of the mild steel and is given by the equation 8 and 9 [23]

$$\frac{x}{m} = KC^{1/n} \quad (8)$$

$$\log \frac{x}{m} = \log K + \frac{1}{n} \log C \quad (9)$$

The fraction $\frac{x}{m}$ in equation 9 has been found to be approximate to the inhibition efficiency of the inhibitor, k and n is constant. Slope is equal to $\frac{1}{n}$ and intercept = $\log k$. Therefore, from equation 9, a plot of \log inhibition efficiency (I %) versus $\log c$ produces a straight line that obeyed Freundlich adsorption isotherm [24], [25].

Table 1: Shows the concentration of the ES and VD extract and inhibition efficiencies at 30°C and 60°C from gasometric method.

Concentration of the inhibitors in(g/l)	Inhibition efficiency (%) from VD extract at		Inhibition efficiency (%) from ES extract at	
	30°C	60°C	30°C	60°C
0.1	23.51	21.11	28.18	22.00
0.2	38.35	30.20	40.25	33.78
0.3	45.13	38.39	49.78	37.97
0.4	51.06	42.29	57.20	46.48
0.5	68.22	54.98	60.38	50.13

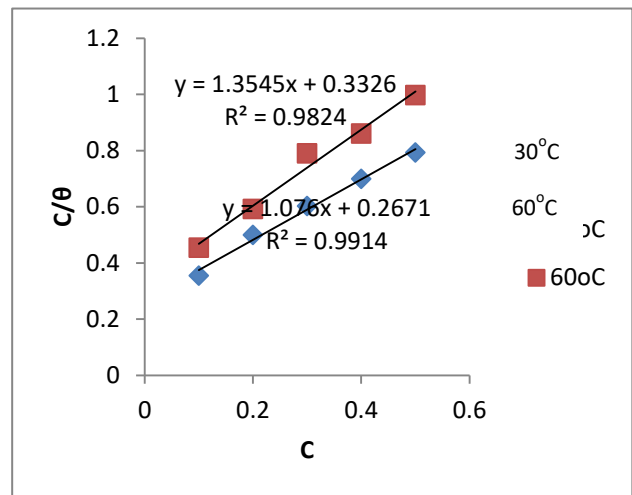


Fig. 1: Langmuir isotherm for the adsorption of ES extract on the surface of mild steel.

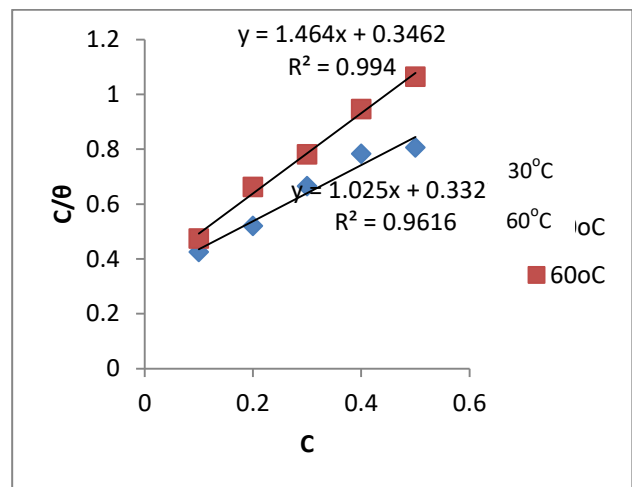


Fig. 2: Langmuir isotherm for the adsorption of VD extract on the surface of mild steel.

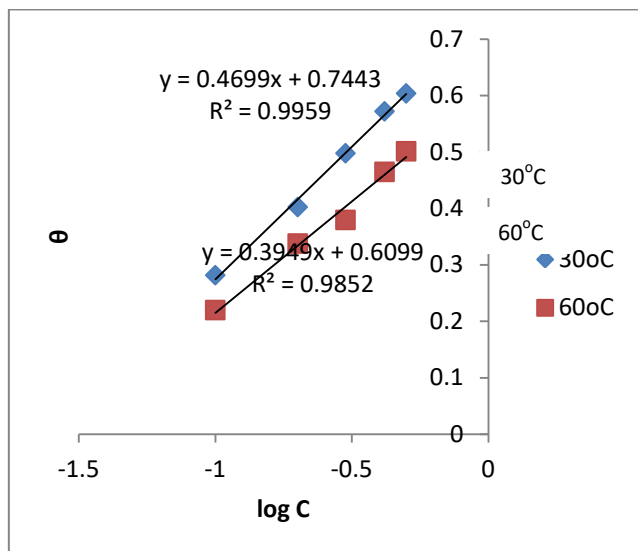


Fig.3: Tempkin isotherm for the adsorption of the of ES extract on the surface of the mild steel.

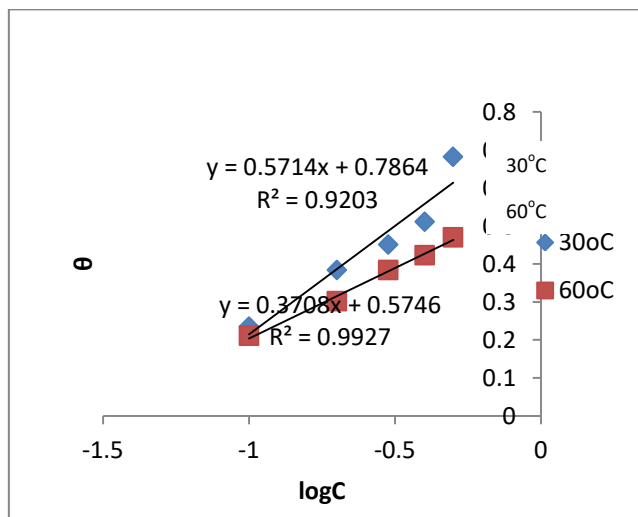


Fig.4: Tempkin isotherm for the adsorption of the leave extract of VD on the surface of the mild steel

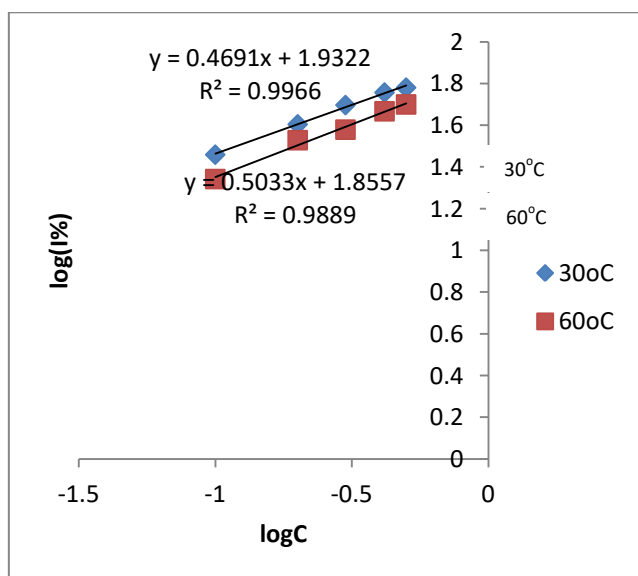


Fig.5: Freundlich isotherm for the adsorption of ES extract on the surface of the mild steel.

VI. THERMODYNAMICS STUDIES

The value of activation energy E_a was calculated using Arrhenius equation.

$$\log \frac{H_{R2}}{H_{R1}} - \frac{E_a}{2.303R} \left(\frac{1}{T_1} - \frac{1}{T_2} \right) \quad (10)$$

Where H_{R1} and H_{R2} are the hydrogen evolution rate at temperature T_1 and T_2 respectively. Table 2 shows the calculated values of E_a for ES and VD extract on the surface of the mild steel. It could be noticed that none of E_a reach up to the threshold value of 80KJmol^{-1} required for chemical adsorption, therefore, the adsorption is by physical adsorption mechanism [26]. Heat of adsorption is approximately equal to enthalpy of reaction ΔH_{ads} . The values of heat of adsorption were calculated using equation (11) [27]-[29].

$$\Delta H_{ads} = 2.303R \left[\log \left(\frac{\theta_2}{1-\theta_2} \right) - \log \left(\frac{\theta_1}{1-\theta_1} \right) \right] \times \frac{T_1 \times T_2}{T_2 - T_1} \quad (11)$$

Where θ_1 and θ_2 are degrees of surface coverage at temperatures, T_1 and T_2 respectively. Table 2: enumerated the values ΔH_{ads} at different concentrations of inhibitors. ΔH_{ads} were found to be negative in all the concentrations of the ES and VD extract showing that the reactions are exothermic. Values of adsorption parameter deduced from Langumir, Tempkin and Freundlich isotherms are recorded in Table 3 and 4. From the Tables the degrees of linearity (R^2) were also close to unity indicating strong adherence of the adsorption of ES and VD extract on the surface of the mild steel. The equilibrium constant of adsorption of ES and VD extract on the surface of the mild steel are related to the free energy of adsorption (ΔG_{ads}) according to equation 11

$$\Delta G_{ads} = -2.303RT \log(55.5)K \quad (11)$$

Where R is the gas constant, T is the temperature, K is the equilibrium constant of adsorption, 55.5 is the molar heat of adsorption of water. Values of K obtained from intercept of Langumir, Tempkin and Freundlich isotherm were used to compute for ΔG_{ads} according to equation 11 and the result in Table 3 and 4.

From the result ΔG_{ads} values were found to be negative and less than the threshold value of -40KJmol^{-1} required for chemical adsorption hence the adsorption of ethanol extract of VD and PS on the surface of mild steel is spontaneous and follows physical adsorption mechanism [30]-[32].

Table 2: Calculated values of E_a and ΔH for ES and VD extract at different concentrations.

Concentr ation of VD and PS inhibito r in g/l.	E_a from ES inhibitor KJ/mol	E_a from VD inhibit or in KJ/mo l	ΔH from ES inhibit or in KJ/mo l	ΔH from VD inhibitor in KJ/mol
0.1	58.37	31.18	-9.14	-3.88
0.2	62.95	41.24	-7.53	-10.39
0.3	53.38	36.38	-13.48	-7.72
0.4	48.46	38.30	-12.05	-9.91
0.5	44.26	37.42	-11.64	-17.05

Table 3: Langmuir, Tempkin and Freundlich adsorption isotherm parameters for adsorption of ES extract on the surface of the mild steel.

Temperature (°C)	K _{ads}	Slope	ΔG (kJmol ⁻¹)	R ²
Langmuir				
30	3.7439	1.0760	-6.7635	0.9914
60	3.0069	1.3545	-8.0733	0.9824
Tempkin				
		a		
30	35.0106	-2.4531	-9.3756	0.9959
60	38.4769	-2.9154	-9.7524	0.9852
Freundlich				
30	85.5067	0.4691	-11.7792	0.9966
60	71.7533	0.5033	-12.8836	0.9889

Table 4: Langmuir and Tempkin adsorption isotherm parameters for adsorption of ethanol extract of VD.

Temperature (°C)	k _{ads}	Slope	ΔG (KJ/mol)	R ²
Langmuir				
30	3.0095	1.0250	-7.3444	0.9616
60	2.8880	1.4640	-8.1840	0.9940
Tempkin				
		a		
30	23.7903	-2.0151	-9.5141	0.9203
60	34.7536	-3.1050	-9.5870	0.9927

VII. CONCLUSION

ES and VD extract showed inhibitive effect on corrosion of mild steel in acidic environment. Inhibition efficiency increase with an increase in inhibitor concentration for both extracts. The adsorptions of ES extract on the surface of the mild steel followed Langmuir, Tempkin and Freundlich while that of VD extract obeyed langmuir and Tempkin adsorption isotherms. ES extract proved to be better corrosion inhibitor than VD extract since it has higher inhibition efficiency. Finally, the mechanism of physical adsorption was proposed from the calculated values of E_a, ΔH_{ads}, and ΔG_{ads}, obtained.

ACKNOWLEDGMENT

We are grateful to Prof. V.I.E. Ajiwe, who went through the work and made some correction. Again, our gratitude goes to all laboratory technologists of Pure and Industrial Chemistry Department, Nnamdi Azikiwe University, Awka, Anambra State, for their assistance during the experiment.

REFERENCES

- Corrosion the free Encyclopedia en.wikipedia.org/wiki/corrosion. Retrieved on 30/1/2013
- A. A. EL-Meligi (2010). Corrosion prevention strategies as a crucial need for decreasing environmental pollution and saving Economy. *Corr. Sci.*, 2: 22-23
- A. Noor Ehteram (2008). Comparative study on the corrosion inhibition of mild steel by aqueous extract of fenugreek seeds and leaves in acidic solutions. *Journal of Engineering and Applied Science*, 3(1):23-30
- H. P. Sachin, M. H. Moinuddin Khani, S. Raghavendra and i, N. S. Bhujangaiah (2009). L dopa as corrosion inhibitor for mild steel in mineral acid. *Open Electrochemistry Journal*, 1:15-18

- P.C. Okafor, E. E. Ebenso and U. J. Ekpe (2010). Azadirachta Indica extract as corrosion inhibitor for mild steel in acidic medium. *Int. J. Electrochem. Sci.*,5(2010):978-993
- R. Saratha, S.V. Pyriya and P. Thilagavathy (2009).Investigation of citrus aurantifolia leaves extract as corrosion inhibitors for mild steel in 1M HCl. *E- Journal of Chem.*, 6(3):785-795
- I. M. Iloamaeke, T. U. Onuegbu, V.I.E. Ajiwe and U. C. Umeobika (2010). Corrosion inhibition of mild steel by *Pterocarpus soyauxii* leaves extract in HCl medium. *Int. J. of Plant and Environmental Sci.*,2(3):22-28
- R. and Vasudha V. G. (2010). *Emblca Officinalis* (Indian Gooseberry) leaves extract as corrosion inhibitor for mild steel in HCl medium. *E-Journal of Chem.*, 7(3): 677-684
- S. Ananda Louise Sathiyathanan, M. Selvanayagam, S. Mohanan, and N. Palaniswamy (2005). Corrosion inhibition of mild steel by ethanolic extract of *Ricinus Communis* leaves. *Indian Journal of Chemical Tech.*, 12:356-360
- K. Orubite Okorosaye, I. R Jack, M. Ochei, and O.Akaranta (2007). Synergistic effect of potassium iodide on corrosion inhibition of mild steel in Hcl medium by extract of *Nypa friuticans wurmb*. *J. of Appl. Sci. and Enviro. Mange.*, 11(2):27-31
- R.Saratha, M. Saranya Devi, H. N. Meenakshi, and R. Shyamala (2011). Enhanced corrosion resistance of Tecoma Stans extract on Mild steel in 0.5M H₂SO₄ solution. *Int. J. Of Current Research*, 2(1): 092-096
- M. A. Quraishi, Dileep Kumar, Yadar and Ishtiaque Ahamad (2009). Green Approach to corrosion inhibition by Black pepper extract in hydrochloric acid solution. *The Open Corr. Journal*, 2:56-60
- P. Arora, S.Kumar, M. N. Sharma, and S. P. Mathur (2007). Corrosion inhibition of aluminum by *Capparius deciduus* in acid medium. *E- J. of Chem.*, 4(4):450-456
- R. Saratha, and V. G. Vasudha, (2009). Inhibition of mild steel corrosion in 1N H₂SO₄ medium by acid extract of *Nyctanthes abortristic* leaves. *E- Journal of Chem.*, 6(4):1003-1008)
- Ambrish Singh and V. K. Vasudha, and M. A. Quraishi (2010). Aqueous extract of Kalmegh (*andrographis paniculata*) leaves as green corrosion inhibitor for mild steel in HCl solution. *Inter. J. of Corr.*, vol 2010 article ID 275983
- S. A. Umoren, E. E. Ebenso, P. C. Okafor, U.J. Ekpe, and O. Ogbobe, (2006). Effect of halide on the corrosion inhibition of aluminum in Alkaline medium using polyvinyl alcohol. *Journal of Appl. Polmeric Sci.*, 103:2810-2816
- S. A. Umoren, O. Ogbobe, I. O. Igwe and E. E. Ebenso (2008). Inhibition of mild steel in acid medium using synthetic and natural occurring polymers and synergistic halide additive. *Corr. Sci.*, 50: 1998-2006
- S. B. Ulaeto, U. J. Ekpe, M. A. Chidiebere, E. E. Oguzie, (2012). Corrosion inhibition of mild steel in HCl by acid extract of *Eichhornia crassipers*. *Int. J. of Material and Chem.*, 2(4): 156-164
- I. B. Obot, S. A. Umoren, and N. O. Obi- Egbedi (2011). Corrosion inhibition and adsorption behavior for aluminum by extract of *amingera robusta* in HCl solution: Synergistic effect of Iodide ions. *J. Mater Enviro. Sci.*, 2(1):60-70
- Y. K. Agrawal, J. D. Shah, M. N. Desai, and N. K Shah (2003). Schiff bases ethylene as corrosion inhibitors of zinc in sulphuric acid. *Corrosion sci.*, 46: 633-651
- M. Abdullah (2004). Antibacterial drugs as inhibitors for corrosion of aluminum in HCl solution. *Corrosion Sci.*, 46:1981-1998
- A.Y. El.Etre (2003).Inhibition of aluminum corrosion using *opuntia* extract. *Corrosion sci.*, 45:2485-2495
- K. K. Sharma, and L. K. Sharma, *A textbook of Physical Chemistry*, 4th edition, New Delhi Indian: Vikas publishing house Ltd,1999, p 608
- S. A.Umoren, O. Ogbobe, E. E. Ebenso, and U. J. Ekpe (2006). Effect of halide ions on the corrosion inhibitor of mild steel in acidic medium using polyvinyl alcohol. *Pigment and Resin Technology*, 35(5):284-292.
- S.A.Umoren, U. M. Eduok, and E. E. Oguzie (2008). Corrosion inhibition of mild steel in 1M H₂SO₄ by Polyvinyl Pyrrolidone and synergistic iodide additive. *Portugaluae Electrochemica Acta*, 26(6): 533-546
- P. Deepa Rani, and S. Selvaraj (2010). *Emblca Officinalis* (AMLA) leaves extract as corrosion inhibitor for copper and its alloy (Cu-272N) in natural Sea Water: *Archived of applied Science Research*, 2(6): 140-150



27. N. O. Eddy, P. Ekwumegbo, and S. A. Odemelam, (2008). Inhibition of the mild steel in H_2SO_4 by 5-amino-1-cyclopropyl-7-(3r,5s)-dimethylpiperazin-1-yl]-6,8-difluoro-4-oxo-quinoline-3-carboxylic acid. *Inter journal of physical science*, 3(2):1-6
28. P.C. Okafor, E. E. Ebenso, and J. U. Ekpe (2010). *Azadirachta indica* extract as corrosion inhibitor for mild steel in acid medium. *Inter.Journal of Electrochemical Science*, 5: 978-993.
29. M. A Quraish, Dileep Kumar Yadaar and Ishtiague Ahamud (2009). Green Approach to corrosion Inhibition by black pepper extract in HCl. *Open Corrosion Journal*, 2: 56-60.
30. N. O. Eddy, and A. S Ekop (2007). Inhibition corrosion of zinc in 0.1M H_2SO_4 by 5-amino-1-cyclopropyl-7-[(3r, 5s) 3, 5-dimethylpiperazin-1-yl] -6, 8-difluoro-4-oxoquinolne-3-carboxylic acid. *MSAIJ*, 4(1):2008-2016
31. M. M. Ihebrodike, A. A. Uroh, K. B. Okeoma, and G. A. Alozie (2010). The inhibitive effect of *Solanum melongena* L. leaves extract on the corrosion of aluminum in H_2SO_4 . *African Journal of Pure and Applied Chem.*, 4(8): 158-165.
32. R.Saratha, Saranya Devi, H. N. Meenakshi, and R. Shyamala, (2011). Enhanced corrosion resistance of *Tecoma stans* extract on the mild steel in 0.5M H_2SO_4 solution. *Inter. Journal of current Research*, 2(1): 092-096.